


AD No. 31225  
ASTIA FILE COPY

Navy Contract Number N6ori-17, T.O. IV  
ONR Project Number NR 058 059

Tech. Report No. 12 Project RF-280

## THE OHIO STATE UNIVERSITY RESEARCH FOUNDATION

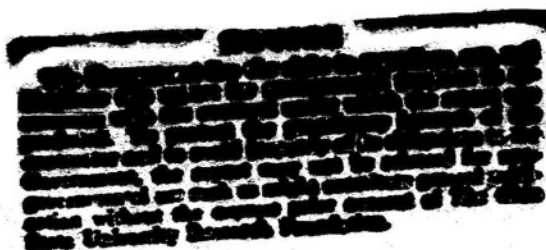

THIS REPORT HAS BEEN DELIMITED  
AND CLEARED FOR PUBLIC RELEASE  
UNDER DOD DIRECTIVE 5200.20 AND  
NO RESTRICTIONS ARE IMPOSED UPON  
ITS USE AND DISCLOSURE.

**DISTRIBUTION STATEMENT A**

APPROVED FOR PUBLIC RELEASE;  
DISTRIBUTION UNLIMITED.

**THE REACTION OCCURRING ON THORIATED CATHODES**

by

**Michael Hoch and Herrick L. Johnston**

**TR 280-12**

**April 1, 1954**

**Technical Report**

**Cryogenic Laboratory  
Department of Chemistry  
The Ohio State University  
Columbus 10, Ohio**

## FOREWORD

This work was carried out at The Ohio State University Cryogenic Laboratory under contract with U.S. Navy, Office of Naval Research Contract Number N6ori-17, Task Order IV, ONR Project Number NR 058 039, with The Ohio State University Research Foundation. This report covers information obtained during the study entitled: "High Temperature Thermodynamics of Inorganic Substances." It represents the 12th Technical Report of this series.

Director - - - Herrick L. Johnston

Editor - - - Marjorie Lassette

## TABLE OF CONTENTS

	<u>Page</u>
ABSTRACT . . . . .	1
INTRODUCTION. . . . .	2
APPARATUS AND EXPERIMENTAL PROCEDURE . . .	3
EXPERIMENTAL RESULTS AND DISCUSSION OF DATA. .	4
Vapor Pressure Data . . . . .	4
High-Temperature X-Ray Diffraction Data . . . . .	7
CONCLUSION . . . . .	9
ACKNOWLEDGEMENTS . . . . .	9
REFERENCES . . . . .	10

## ABSTRACT

The vapor pressure of thorium dioxide was determined by the method of Knudsen, between 2398° and 2677°K.  $\text{ThO}_2$  vaporizes mostly undissociated as  $\text{ThO}_2(\text{g})$ , the heat of vaporization being  $\Delta H_{298}^\circ = 170 \pm 1$  kcal/mole. Some of the material (2-10%) vaporizes as  $\text{ThO}$ . No reaction occurs between  $\text{ThO}$  and W. The study of the reaction  $\text{Th}(\text{l}) + \text{ThO}(\text{s}) \rightleftharpoons 2\text{ThO}(\text{s})$  by a high temperature x-ray diffraction technique showed the formation at 2050°K of solid  $\text{ThO}$ . The  $\text{ThO}$  has a cubic, face-centered lattice, with  $a = 4.31 \text{ \AA}$ . The formation of thorium on the thoriated cathodes is thus due to the decomposition of the  $\text{ThO}_2$  to  $\text{ThO}$  at 2500°K and above; the  $\text{ThO}$  disproportionates to  $\text{Th}$  and  $\text{ThO}_2$  on cooling to 2000°K.

## INTRODUCTION

The reaction between  $\text{ThO}_2$  and W, or the question of what occurs on a thoriated cathode, how the thorium (which is assumed to be the emitter) is formed, is still unsolved, although many investigators have attacked the problem. All the work was done, however, on filaments, and the main interest was to improve the emission. Langmuir<sup>1</sup> reported a heat of vaporization of  $\text{ThO}_2$  of 184 kcal and a heat of reduction of 138 kcal. Shapiro<sup>2</sup> measured rates of evaporation with or without emission and found them equal. He obtained a heat of vaporization for  $\text{ThO}_2$  of 171 kcal. Fan<sup>3</sup> studied the emission of  $\text{ThO}_2$  alone, and of  $\text{ThO}_2 + \text{W}$ , and found them equal. He measured a heat of vaporization of 184 kcal for  $\text{ThO}_2$  and 46 kcal for Th. The emission characteristics of thoriated cathodes have been reviewed by Danforth.<sup>4</sup>

In this work we first determined the rate of evaporation of  $\text{ThO}_2$  by the Knudsen effusion method. The material vaporized was collected on two collectors: a cold collector at room temperature and a hot collector, the temperature of which was about  $2000^\circ\text{K}$ . The purpose of the two collectors was the following: If only molecules which are stable at room temperature (such as  $\text{ThO}_2$  or Th) evaporate, then the x-ray diffraction patterns of the material on the two collectors should be identical. If a molecule which is unstable at room temperature (such as ThO) evaporates, on the cold collector we will obtain an amorphous substance due to the rapid cooling of the gas molecule (similar to the case of  $\text{SiO}$ )<sup>5</sup>. If this molecule hits the hot collector, the temperature of which is low enough that the ThO molecule is not stable, but high enough that the ThO molecule can disproportionate to Th and  $\text{ThO}_2$ , then the x-ray diffraction patterns of the materials on the two collectors should be different. The chemical analyses of the two molecules would be identical.

The rate of evaporation over a  $\text{ThO}_2 + \text{W}$  mixture was determined in a manner similar to that used over  $\text{ThO}_2$ .

The reaction  $\text{ThO}_2(\text{s}) + \text{Th}(\text{l}) \rightleftharpoons \text{ThO}(\text{s})$  was studied by taking x-ray diffraction patterns at elevated temperatures. The formation of a new compound is shown by the appearance of a

new set of diffraction lines. From the new diffraction pattern the lattice constant and crystal structure of the compound can be determined.

## APPARATUS AND EXPERIMENTAL PROCEDURE

Two tantalum Knudsen cells, dimensions 0.5 in. diameter, 0.75 in. high with an orifice diameter of 0.0625 in., were used for the vapor pressure measurements. The area of the orifice was corrected for thermal expansion by using the thermal expansion coefficient of tantalum determined previously in this Laboratory.<sup>6</sup> ThO<sub>2</sub> was introduced into the first cell; after the data on pure ThO<sub>2</sub> were taken, an equimolecular mixture of ThO<sub>2</sub> and W was introduced into the same cell. Into the second cell only the ThO<sub>2</sub> + W was introduced, and data taken. Both cells were degassed for two hours at 2000° C before the runs were made.

A new metal vapor-pressure cell was built, similar to the one used on our calorimeter,<sup>7</sup> and shown in Fig. 1. The power was supplied by a 20 kw General Electric heater, equipped with grid control. The temperature was measured with a disappearing-filament optical pyrometer, calibrated against a standard tungsten-ribbon lamp. The standard tungsten lamp had been calibrated by the National Bureau of Standards and, in the range of the present investigation, was reported to have a maximum uncertainty of 8°.

When the cells were degassed, the initial heating was only about 5 seconds (negligible compared to the length of the run), due to the high pumping speed. The power input into the cell was very constant, and possible small temperature fluctuations were masked in the uncertainty of the temperature readings. Thus the temperature was taken as the average of the readings, and straight time was used to compute the pressures.

In the temperature range where the experiments were carried out, tantalum, the cell material, has a low though measurable vapor pressure. Blank runs on the empty cells were carried out, and the weight losses of thorium dioxide were corrected for the weight loss of the empty cell. The weight loss of the empty cell was always less than 10 percent of the weight loss due to thorium dioxide.



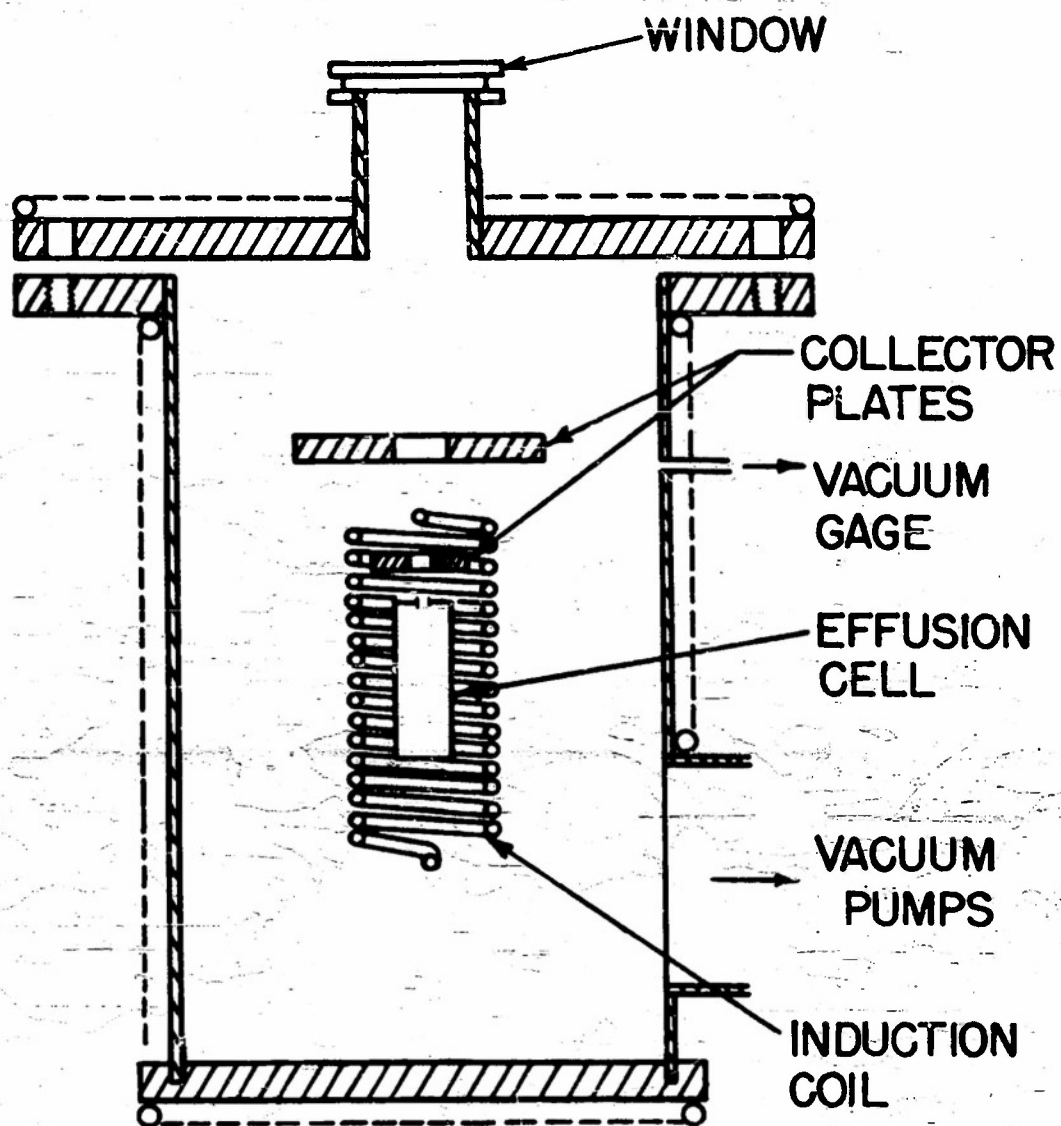


FIGURE 1

To correct for the thickness of the effusion hole (.01 in.) all weight losses due to  $\text{ThO}_2$  were multiplied by the factor  $\frac{1}{0.89}$  = 1.1236.<sup>8,9</sup>

The cold collector plates were made of pyrex 1.5 in. in diameter with a 0.25 in. hole in the middle. The hot collector was made of tantalum, 0.5 in. in diameter, with several 0.0625 in. holes drilled into it and several slits in the side to regulate its temperature. The material from the cold collector was scraped off, fastened with some "radio cement" to a thin glass rod, and x-ray diffraction patterns photographed in the Norelco-Phillips x-ray camera. The evaporating material slowly filled up the holes of the hot collector plates. The material was broken off with a pair of tweezers and put into the x-ray diffraction camera.

The high-temperature x-ray diffraction patterns were photographed in our high-temperature camera.<sup>10</sup> The technique used was the same as that described elsewhere<sup>5,11</sup> except that the x-ray diffraction patterns were obtained in a high vacuum, with an exposure time of 30 minutes. The use of a vacuum was necessary because, at the high temperatures involved, arcing occurred in helium and argon atmospheres.

The thorium dioxide was obtained from the Maywood Chemical Works, the thorium from the Fairmount Chemical Co., and the tungsten from the Callite Tungsten Corp.

## EXPERIMENTAL RESULTS AND DISCUSSION OF DATA

### Vapor Pressure Data

The experimental data for pure  $\text{ThO}_2$  are presented in Table I, and those for the  $\text{ThO}_2 + \text{W}$  mixture are given in Table II. The data from the two tables are plotted in Fig. 2. The pressure was calculated from the rate of effusion, using the equation  $p = m\sqrt{2\pi RT/M}$ , where  $p$  is the pressure in atmospheres,  $R$  is the molar gas constant,  $T$  is the absolute temperature,  $m$  is the rate of effusion in g/sq. cm./sec. and  $M$  is the molecular weight of the vapor.

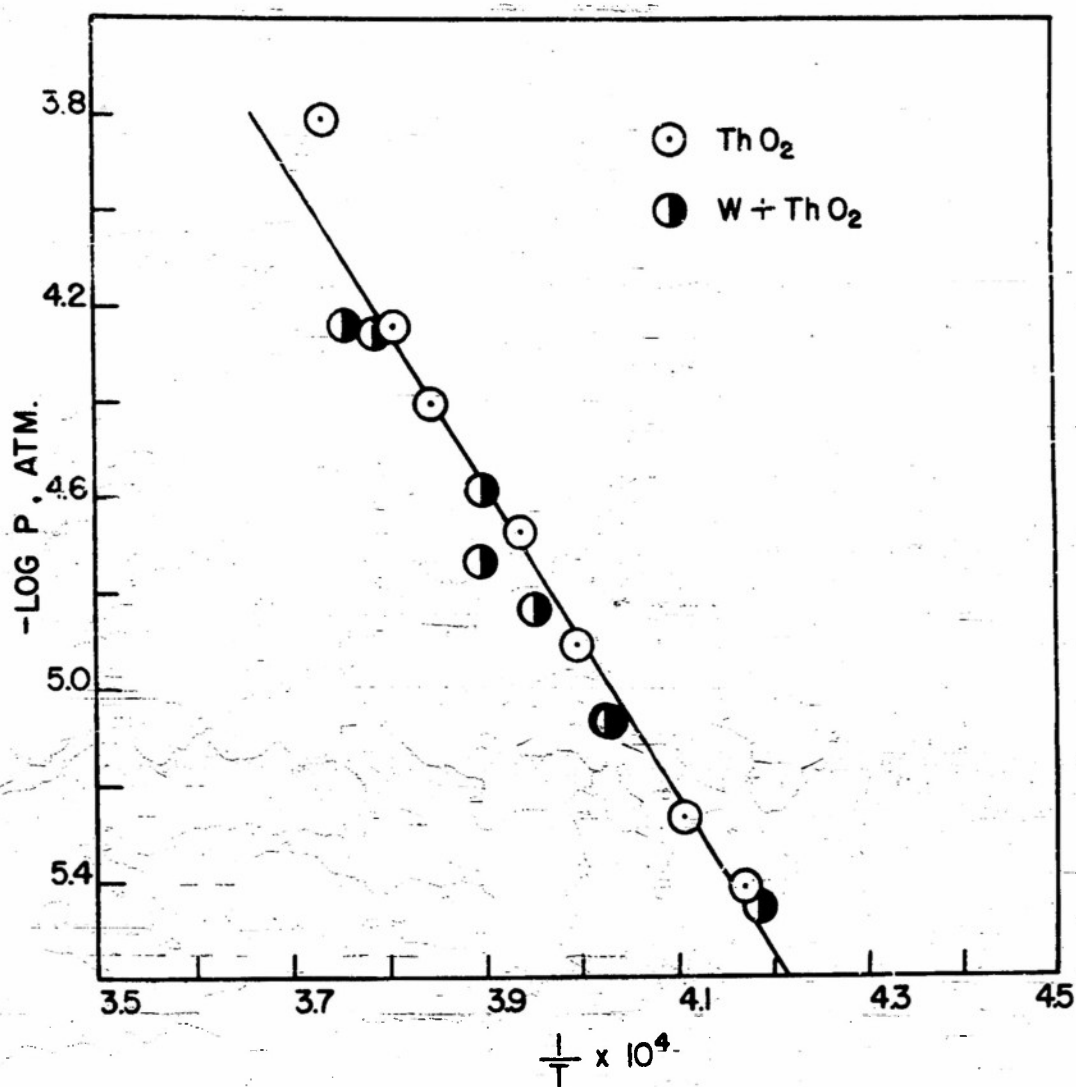


FIGURE 2

TABLE I

VAPOR PRESSURE OF  $\text{ThO}_2$ 

Run	Temp (°K)	Effective Time (Sec.)	Area (cm <sup>2</sup> )	Wt. Loss (g.)	Evaporation Rate (g/cm <sup>2</sup> /sec) $\times 10^3$	P (atm.) $\times 10^6$	-log P
1	2398	25200	0.0195	0.0250	5.7046	3.878	5.411
6	2435	14400	0.0196	0.0197	7.8506	5.378	5.269
5	2502	7200	0.0196	0.0223	17.805	12.363	4.908
3	2539	10800	0.0196	0.0573	30.415	21.275	4.672
4	2600	7200	0.0196	0.0702	55.897	39.565	4.403
2	2625	7200	0.0196	0.1017	80.859	57.510	4.240
7	2676	1800	0.0196	0.0683	217.02	155.839	3.807

TABLE II

VAPOR PRESSURE OF  $\text{TiO}_2 + \text{W}$ 

Run	Temp. (°K)	Effective Time (Sec.)	Area (cm <sup>2</sup> )	Wt. Loss (g.)	Evaporation Rate (g/cm <sup>2</sup> /sec) $\times 10^5$	P (atm.) $\times 10^6$	-log P
1	2389	25200	0.0195	0.0228	5.2049	3.532	5.452
6	2481	5400	0.0196	0.0116	12.376	8.557	5.068
8	2484	9000	0.0196	0.0196	12.472	8.629	5.064
5	2529	4500	0.0196	0.0166	21.132	14.753	4.831
3	2564	3600	0.0196	0.0283	37.087	26.071	4.584
7	2566	3600	0.0196	0.0166	26.402	18.567	4.731
4	2639	2910	0.0196	0.0397	78.030	55.643	4.255
2	2661	4500	0.0196	0.0634	80.577	57.700	4.239

The rates of evaporation are equal in both cases, indicating that no reaction between W and ThO<sub>2</sub> occurs. The x-ray diffraction photographs taken of the material condensed on the cold collector showed only the ThO<sub>2</sub> pattern. The material from the hot collector showed the ThO<sub>2</sub> pattern very strongly, and the Th pattern weakly. The visual intensity ratio was from 50:1 to 10:1. This indicates that ThO<sub>2</sub> vaporizes as ThO<sub>2</sub>(g) with a slight dissociation to ThO.

If ThO<sub>2</sub> would vaporize completely as ThO and O, and then recombine on the collector plates, the x-ray diffraction pattern of the material from the cold collector would have, besides ThO<sub>2</sub> lines, a strong amorphous background, which it does not have. No diffraction lines of tungsten or tungsten oxide were found on any collector.

To obtain  $\Delta H$  and the equation for the vapor pressure, our data was treated by a sigma plot. The necessary specific heat data were taken from Kelley<sup>12</sup> for solid ThO<sub>2</sub> ( $C_p = 15.84 + 2.88 \times 10^{-3} T - 1.60 \times 10^{-5} T^2$ ), and we estimated, for gaseous ThO<sub>2</sub>,  $C_p = 10.5$  cal/mole/deg. Thus we obtain  $\Delta H_{298}^0 = 170.3$  kcal/mole, and

$$\Delta H = 172,491 - 5.34 T - 1.44 \times 10^{-3} T^2 - 1.60 \times 10^{-5} T^{-1}.$$

The vapor pressure can be expressed by the relation

$$\log p(\text{atm}) = -37695 T^{-1} - 7.82 \times 10^{-4} T + 12.145.$$

A comparison of our data with Shapiro's shows that the heats of vaporization agree very well; however, our pressures are about 40 times as large as his. At 2000°K we have  $4 \times 10^{-6}$  mm and Shapiro has  $1 \times 10^{-7}$  mm. The discrepancy corresponds to a temperature difference of 200°, due probably to the fact that the loosely attached ThO<sub>2</sub> does not reach the temperature of the heating wire, although the pyrometer gives the temperature of the latter.

#### High-Temperature X-Ray Diffraction Data

The high temperature x-ray diffraction studies of an equimolar mixture of Th + ThO<sub>2</sub> showed, at 1850°C, the almost complete disappearance of the ThO<sub>2</sub> and Th diffraction line and the appearance of a new set of diffraction lines. On cooling


TABLE III  
X-RAY DIFFRACTION LINES OF ThO AT 1850°C  
( $a_0 = 4.31 \text{ \AA}$ )

$\sin^2 \Theta$	$d(\text{in } \text{\AA})$	Indices h, k, l
.0967	2.47	1, 1, 1
.1280	2.14	2, 0, 0
.2540	1.52	2, 2, 0
.3491	1.30	3, 1, 1
.3785	1.25	2, 2, 2
.5238	1.06	4, 0, 0
.6229	.974	3, 3, 1

this new set of diffraction lines disappeared and the Th and ThO<sub>2</sub> pattern reappeared. The new diffraction lines could be indexed with a face-centered cubic pattern with  $a_0 = 4.31 \text{ \AA}$ . Interplanar distances are given in Table III. This new diffraction pattern is that of thorium monoxide, indicating that above 1850°C the reaction  $\text{ThO}_2(\text{s}) + \text{Th}(\text{l}) \rightleftharpoons 2\text{ThO}(\text{s})$  goes to the right.

### CONCLUSION

We can now answer the last question, what happens on a thoriated filament, when it is activated at 2600°K, then cooled to 1800°-1900°K. At 2600°K some of the ThO<sub>2</sub> dissociates to gaseous and solid ThO, which disproportionates to Th and ThO<sub>2</sub> on cooling to 1900°K. For the heat of reduction of ThO<sub>2</sub>, Langmuir<sup>1</sup> gave 138 kcal. The heat of formation of ThO<sub>2</sub> from Th and O<sub>2</sub> is 293 kcal.<sup>13</sup> Thus the value of 138 kcal is very probably for the reaction



### ACKNOWLEDGEMENTS

We wish to thank Robert W. Mattox and David P. Dingley, who helped with the vapor-pressure measurements.



## REFERENCES

1. I. Langmuir, Phys. Rev. 22, 357 (1923).
2. E. Shapiro, J. Am. Chem. Soc. 74, 5233 (1952).
3. H. Y. Fan, J. Applied Phys. 20, 682 (1949).
4. W. E. Danforth, Advances in Electronics 5, 170-210 (1953).
5. M. Hoch and H. L. Johnston, J. Am. Chem. Soc. 75, 5224 (1953).
6. J. W. Edwards, R. Speiser, and H. L. Johnston, J. Applied Phys. 22, 424 (1951).
7. M. Hoch and H. L. Johnston, to be published.
8. P. Clausing, Ann. Physik. 12, 961 (1932).
9. S. Dushman, "Scientific Foundations of Vacuum Technique," John Wiley and Sons, New York, N. Y., 1949, 96 pp.
10. J. W. Edwards, R. Speiser, and H. L. Johnston, Rev. Sci. Instr. 20, 343 (1949).
11. M. Hoch and H. L. Johnston, TR 280-13, this contract.
12. K. K. Kelley, "High Temperature Heat Content and Entropy Data for Inorganic Compounds," Bur. of Mines Bull. 476 (1949).
13. E. J. Huber, C. E. Halley, Jr., and E. H. Meierkord, J. Am. Chem. Soc. 74, 3406 (1952).

List Revised October 1, 1953

RF Project 280

DISTRIBUTION LIST FOR TECHNICAL REPORTS  
N6onr-17 Task Order IV  
Office of Naval Research  
NR 358 039

<u>Addressee</u>	<u>No. of Copies</u>
Commanding Officer U. S. Navy Office of Naval Research Branch Office 495 Summer Street Boston 10, Mass	1
Commanding Officer U. S. Navy Office of Naval Research Branch Office The John Crerar Library Building Tenth Floor, 86 E. Randolph St. Chicago 1, Illinois	2
Commanding Officer U. S. Navy Office of Naval Research Branch Office 1030 N. Green Street Pasadena 1, California	1
Commanding Officer U. S. Navy Office Branch Office 801 Donahue Street San Francisco 24, California	1
Commanding Officer U. S. Naval Ordnance Test Station Inyokern, China Lake, California	1
Commanding Officer Naval Powder Factory Indian Head, Maryland	1

List Revised 10/1/53

RF Project 280

Addressee

No. of Copies

Office of Naval Research  
346 Broadway  
New York 13, N. Y.

1

Office of Naval Research  
Navy Department  
Washington 25, D. C.  
Attn: Project Status, Code N482

2

Officer-in-Charge  
Office of Naval Research, Branch Office  
Navy No. 100  
Fleet Post Office  
New York, N. Y.

2

Chief of Naval Research  
Office of Naval Research  
Washington 25, D. C.  
Attn: Chemistry Branch

2

Chief of the Bureau of Aeronautics  
Navy Department  
Washington 25, D. C.  
Attn: Code TD-4

2

Chief of the Bureau of Ordnance  
Navy Department  
Washington 25, D. C.  
Attn: Code Rexd

2

Chief of the Bureau of Ships  
Navy Department  
Washington 25, D. C.  
Attn: Code 330

2

Director, Naval Research Laboratory  
Washington 25, D. C.  
Attn: Tech. Info. Officer

6

List Revised 10/1/53

RF Project 280

Addressee

No. of Copies

Director, Naval Research Laboratory  
Washington 25, D.C.  
Attn: Chemistry Division

2

Office of the Quartermaster General USA  
Research and Development Branch  
Chemistry and Plastics Section  
Washington, D.C.  
Attn: Mr. Wm. McC. Lee, Chief

1

Joint Research and Development Board  
1712 G Street, N.W.  
Washington, D.C.  
Attn: Mr. R.L. Clark, Program Division

1

Research and Development Group  
General Staff, Department of the Army  
Washington 25, D.C.  
Attn: Dr. W.T. Read, Scientific Advisor

1

Research and Development Board  
Pentagon, Room 3E123  
Washington 25, D.C.  
Attn: Technical Reference Section

1

Commanding General  
Army Air Forces  
Pentagon Bldg.  
Washington 25, D.C.

1

Commanding General  
Air Materiel Command  
Wright-Patterson Air Force Base  
Dayton, Ohio  
Attn: Office of Air Research (MCRRXS)  
Power Plant Laboratory (MCREXP-3)  
Central Air Document Office (MCLDSD)

3

Last Revised 10/1/53

RF Project 280

<u>Addressee</u>	<u>No. of Copies</u>
National Bureau of Standards Thermochemistry Laboratory Washington 25, D.C. Attn: Dr. F.W. Brickwedde	1
Aerojet Engineering Corporation Azusa, California Attn: Dr. F. Zwicky	1
Battelle Memorial Institute 505 King Avenue Columbus 1, Ohio Attn: Mr. J.B. Holding	1
Los Alamos Scientific Laboratory P.O. Box 1663 Los Alamos, New Mexico Attn: Dr. J.F. Lemons	1
California Institute of Technology Jet Propulsion Laboratory GALCIT Pasadena 4, California	1
Carnegie Institute of Technology Department of Chemistry Metals Research Laboratory Pittsburgh, Pennsylvania Attn: Dr. E. Birchenall	1
Carnegie Institute of Technology Department of Chemistry Pittsburgh 13, Pennsylvania Attn: Dr. F.D. Rossini	1
John Hopkins University Applied Physics Laboratory 9621 Georgia Avenue Silver Springs, Maryland Attn: Dr. L.R. Hofstad	1

List Revised 10/1/53

RF Project 280

Addressee

No. of Copies

Princeton University  
Princeton, New Jersey  
Attn: Project SQUID

1

Ohio State University Research Foundation  
Columbus 10, Ohio

1

Ohio State University  
Department of Chemistry  
Columbus 10, Ohio  
Attn: Prof. H. L. Johnston

-1

ASTIA Document Service Center  
Knott Building  
Dayton 2, Ohio

5

Office of Technical Services  
Department of Commerce  
Washington 25, D. C.

Office of Secretary of Defense  
Pentagon, Room 3D1041  
Washington 25, D. C.  
Attn: Library Branch (R and D)

1

Dr. A. D. Horney  
Office Scientific Research USAF  
R and D Command, Box 1395  
Baltimore, Maryland

1

Dr. C. W. Beckett, Acting Chief  
Thermodynamics Section  
National Bureau of Standards  
Washington 25, D. C.

1

Defense Research Member  
Canadian Joint Staff  
1746 Massachusetts Ave., N. W.  
Washington, D. C.

1

List Revised 10/1/53

RF Project 280

Addressee

No. of Copies

Naval Ordnance Laboratory  
White Oak  
Silver Spring, Maryland  
Attn: HL Division

1

Naval Ordnance Laboratory  
White Oak  
Silver Spring, Maryland  
Attn: EF Division

1